

Title	宙吊りグラフェン・フォノン結晶 (GPnC)における熱輸送の研究
Author(s)	HAQUE, MAYEESHA MASRURA
Citation	
Issue Date	2020-09
Type	Thesis or Dissertation
Text version	ETD
URL	http://hdl.handle.net/10119/17015
Rights	
Description	Supervisor:水田 博, 先端科学技術研究科, 博士

Thermal Transport in Suspended Graphene Phononic Crystal (GPnC)

Doctor of Science (Materials Science)

Haque Mayeesha Masrura, s1620426, Mizuta Lab (JAIST)

a. Research content

Background

With the advances in the field of electronics, it has become relevant to reflect on the ever-growing problem of management of waste heat and probe further into nanoscale heat transport as the devices are being vigorously scaled down to tens of nanometers. The physical entity that can help create thermal blockade is now defined as phononic crystals (PnCs) in the community- the terminology rooted into the word 'phonon' which represents the quanta of atomic vibration in materials. RFabrication of PnCs has become a subject of interest for the potential it offers for heat propagation control. Fabrication of intricate nanopatterns on materials like silicon and steel has long since been realized with the optimization of various focused ion beam (FIB) techniques. However, it has been reported that, with superior physical and mechanical properties i.e. Young's modulus (~ 1 TPa) and Debye temperature (~ 1900 K) graphene offers better flexibility and control of phonon contributions. In this work, we have reflected on the asymmetry in thermal transport in graphene phononic crystals as an initial study to understand thermal rectification characteristics in nanoscale devices.

Summary of results

First, the dispersion curves and transmission probability of graphene based phononic crystals by configuring different periodicity, porosity and pore shape were studied by Finite Element Method simulations. From the dispersion relations, obvious band flattening or distinct frequency regions were observed where phonon transmission was completely blocked. The analysis showed strong evidence of porosity and pore shape dependency on phononic band gap (PnBG) generation. For circular shaped nanopores, a very small PnBG opens at ~ 0.4 THz only at a high porosity over 0.73 which is extremely difficult to achieve using the current experimental facilities. To address this limitation, cross shaped nanopore pattern was introduced where PnBG opened at a porosity ~ 0.28 . The PnBG was most obvious at ~ 0.9 THz for single nanometer neck length and completely disappeared when it increased to 10 nm indicating that the constrictions due to the narrow neck structure induced phonon modes confinement contributing to the suppression or flattening of the dispersion relation. At similar porosity and unit cell size, snowflake shaped pores exhibited phononic bandgap (PnBG) in gradually higher THz (~ 1.5 THZ) regime as the symmetric placement of the neck

length along all the supercell edges reinforced the phonon confinement. Also, the snowflake shaped nanopattern gives the advantage of having larger neck lengths of ~ 10 nm (fig. 1).

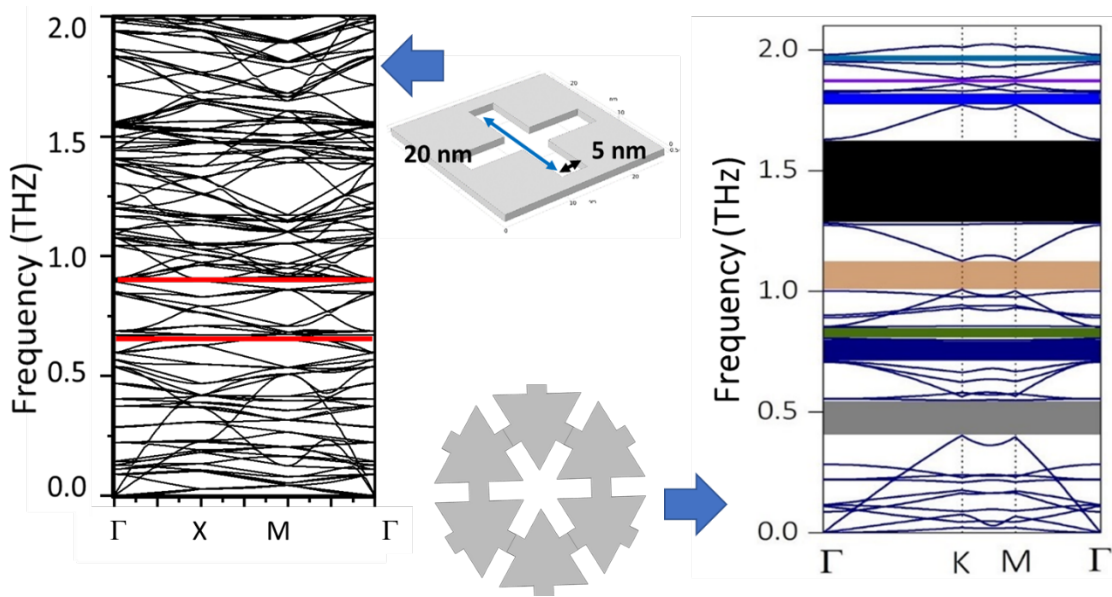


Figure 1: Calculated dispersion relation for cross-shaped and snowflake-shaped nanopores with 28% porosity maintained for both cases.

Next, a reproducible hybrid method was developed and demonstrated to successfully fabricate large area (in μm^2 dimensions) suspended graphene nanomesh (GNM). The GNR are patterned into required dimensions using EBL and later suspended by buffered hydrofluoric acid (BHF) release with gold electrodes acting as a heater. The GNM is fabricated by milling periodic nanopores with as small as ~ 6 nm diameter on the suspended GNR by direct focused helium ion beam milling (HIBM). Taking advantage of the fidelity of HIBM, symmetric and asymmetric graphene nanomesh (GNM) samples were fabricated. As asymmetric GNM with nanopores patterned on half of the total area of the GNR is shown fig. 2(a). The concept of resistive thermometry was used to develop a 4-probe measurement method for thermal characterization of the prepared GNM devices which had 20 nm, 25 nm and 30 nm pitch and ~ 6 nm diameter nanopores. With the base temperature maintained at 150K in a cryogenic vacuum probe station, joule heating was used to generate temperature at the metal electrode. With the measurement setup, resistance at the electrode was measured accurately and the corresponding temperature was calculated. By observing the change in temperature at the heater when there is GNM present, it was confirmed that some of the heat is dissipated through the GNM. The measurement was adopted to observe the trend of thermal dissipation through asymmetric and

symmetric GNM by maintaining similar experimental conditions and most interestingly, characteristics of thermal rectification by introducing asymmetry in the GNM was observed when the heater position was changed. It was observed that the heat transport through the non-meshed area of the patterned GNR to the meshed area is larger compared to when the heater position is swapped and heat transport direction is from the meshed area to the non-meshed area (fig. 2(b))

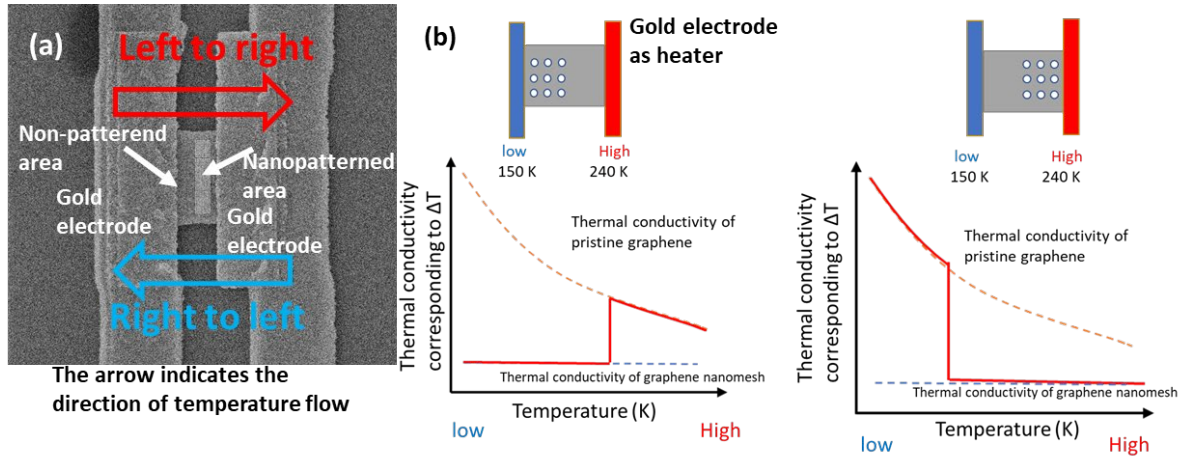


Figure 2: (a) Suspended asymmetric GNM device with nanopores patterned on half of the entire GNR area. (b) Qualitative analysis of asymmetry of thermal transport for the fabricated device.

b. Research objective

Controlling the thermal conductivity of a material independently of its electrical conductivity has always been an intriguing aspect for practical applications of thermoelectric materials. Research on thermal rectification is very important to establish the idea of controlling current induced heat transfer. Numerical simulations performed using continuum models of graphene PnCs in the COMSOL multiphysics platform provided the initial ideas and information to fabricate the GPnC device. A hybrid method by incorporating electron beam lithography (EBL) and helium ion beam milling (HIBM) was developed to fabricate graphene nanomesh (GNM) devices to study their thermal transport characteristics. A 4-terminal thermoelectric measurement method was established to detect the thermal transport through the fabricated GNM. This work provides the initial knowledge and ideas that could provide important information to the community to fabricate graphene based devices for thermal rectification applications.

c. Research accomplishment

Academic journals

1. **Haque Mayeesha Masrura**, Afsal Kareekunnnan, Fayong Liu, Sankar Ganesh Ramaraj, Günter Ellrott, Ahmmed MM Hammam, Manoharan Muruganathan and Hiroshi Mizuta, **Design of Graphene Phononic Crystals for Heat Phonon Engineering**, *Micromachines* 2020, 11(7), 655 / DOI: 10.3 0655
2. Fayong Liu, Zhongwang Wang, Soya Nakanao, Shinichi Ogawa, Yukinori Morita, Marek Schmidt, **Mayeesha Haque**, Manoharan Muruganathan and Hiroshi Mizuta, **Conductance Tunable Suspended Graphene Nanomesh by Helium Ion Milling**, *Micromachines* 2020, 11(4), 387; DOI:10.3390/ mi11040387
3. M. E. Schmidt, T. Iwasaki, M. Muruganathan, **M. Haque**, NH Van, S. Ogawa and H. Mizuta, **Structurally Controlled Large-Area 10 nm Pitch Graphene Nanomesh by Focused Helium Ion Beam Milling**, *ACS Applied Materials & Interfaces* (2018), Vol.10, No. 12, pp. 10362-10368, DOI:10.1021/acsami.8b00427

International conferences

1. **Phononic bandgap formation in single nanometer graphene nanomesh**
M. Haque, M. E. Schmidt, M. Muruganathan, I. Katayama, J. Takeda, S. Ogawa, H. Mizuta
The 1st JAIST World Conference (JWC2018), Nomi, 27-28 February 2018 (Poster presentation)
2. **Phononic Bandgap Engineering in Single Nanometer Graphene Nanomesh**
Mayeesha M. Haque, Marek E. Schmidt, M. Muruganathan, I. Katayama, J. Takeda, S. Ogawa, H. Mizuta
Joint Conference of the 16th International Conference on Phonon Scattering in Condensed Matter (Phonons 2018) and the 4th International Conference on Phononics and Thermal Energy Science (PTES 2018), Nanjing, China, 31 May - 3 June 2018 (Oral presentation)

National conferences (in chronological order)

1. **Effects of structural dimensions on phonon bandgaps in nanopatterned graphene phononic crystals**
Mayeesha M. Haque, Marek E. Schmidt, Takuya Iwasaki, Manoharan Muruganathan, Hiroshi Mizuta
第 78 回応用物理学会秋季学術講演会
2. **Graphene Nanophononics: Sample fabrication and FEM Simulation I**
Mayeesha M. Haque, Seiya Kubo, Marek E. Schmidt, Manoharan Muruganathan, Shinichi Ogawa, Hiroshi Mizuta
第 2 回フォノンエンジニアリング研究会
2018 年 7 月 13 日-14 日、KKR ホテル熱海
3. **Fabrication process and thermal conductivity measurement setup of graphene phononic crystal**
M. Haque, S. Kubo, M. E. Schmidt, M. Muruganathan, S. Ogawa, H. Mizuta
第 79 回応用物理学会秋季学術講演会
2018 年 9 月 18 日-21 日、名古屋国際会議場

Keywords: Graphene phononic crystal, Graphene nanomesh, Helium ion beam milling, Phononic bandgap, Resistive thermometry, Thermal rectification.